



národní
úložiště
šedé
literatury

Study and characterization of natural bentonite modified by Manganese Oxides

Dolinská, S.
2015

Dostupný z <http://www.nusl.cz/ntk/nusl-263112>

Dílo je chráněno podle autorského zákona č. 121/2000 Sb.

Tento dokument byl stažen z Národního úložiště šedé literatury (NUŠL).

Datum stažení: 19.04.2024

Další dokumenty můžete najít prostřednictvím vyhledávacího rozhraní [nusl.cz](http://www.nusl.cz) .

STUDY AND CHARACTERIZATION OF NATURAL BENTONITE MODIFIED BY MANGANESE OXIDES

Silvia DOLINSKÁ¹, Tomáš SCHÜTZ², Ingrid ZNAMENÁČKOVÁ¹,
Lenka VACULÍKOVÁ³

¹Institute of Geotechnics of SAS, Watsonova 45, 040 01 Košice, Slovak Republic

²Ovručská 1, 040 22 Košice, Slovak Republic

³Institute of Geonics of AS CR, Studentska 1768, 708 00 Ostrava-Poruba, Czech Republic
sdolinska@saske.sk, znamenackova@saske.sk

Abstract

The paper describes the preparation of new composite based on relatively cheap natural materials from domestic deposits and synthetically prepared manganese oxides. At first the natural bentonite was simple chemically modified by natrification. The natrification salt Na_2CO_3 is used almost exclusively thanks to its financial accessibility. Then the manganese oxides were precipitated on the surface of activated sodium bentonite particles. The structural changes of bentonite, before and after its modification, were studied by X-ray diffraction analysis and FTIR spectroscopy. The morphology of the bentonites was observed by scanning electron microscopy.

Keywords: *bentonite, natrification, manganese oxides*

(received 24 April 2015, accepted 10 May 2015)


Introduction

The bentonite is a natural clay mineral that is found in many places of the world. Any clay of volcanic origin that contains montmorillonite is referred to as bentonite. It belongs to the 2:1 clay family, the basic structural unit of which is composed of two tetrahedrally coordinated sheets of silicon ions surrounding a sandwiched octahedrally coordinated sheet of aluminum ions. The isomorphous substitution of Al^{3+} for Si^{4+} in the tetrahedral layer and Mg^{2+} or Fe^{3+} for Al^{3+} in the octahedral layer results in a net negative surface charge on the clay. Compared with other clay types, it has excellent adsorption properties and possesses adsorption sites available within its interlayer space as well as on the outer surface and edges (Eren et al., 2008a; Eren et al., 2009b; Fusová et al., 2011a, 2011b). Adsorption of metal ions onto montmorillonite appears to involve two distinct mechanisms: (i) an ion exchange reaction at permanent-charge sites, and (ii) formation of complexes with the surface hydroxyl groups. A composite adsorbent, manganese oxide-coated bentonite, was proposed and studied in this research. The reason for choosing manganese oxides is that relative to Fe or Al oxides, manganese oxides have a higher affinity for many heavy metals (Fan et al., 2005; Eren et al., 2009). Bentonite, which has a high surface area, should provide an efficient surface for the manganese oxide. At the same time, the manganese oxides can improve the heavy-metal adsorption capacity of bentonite.

Materials and methods

The bentonite used in this study originated from the Slovak deposit Stará Kremnička – Jelšový potok. This natural bentonite (B) contains almost monomineral fraction of montmorillonite (> 90 %) with the particles size below 20 μm (Jesenák and Hlavatý, 2000). The particular amount of natural bentonite was

converted to its monoionic sodium form. The natrified bentonite (NaB) was prepared from the slurry, which contained the activating agent (Na₂CO₃) and distilled water to which the bentonite was added. The stabilization took 24 hours at ambient temperature. The final product was dried at 60 °C and then it was mashed manually. Subsequently, the manganese oxide - natural bentonite composite (Mn-B), manganese oxide – natrified bentonite composite (Mn-NaB) and reference sample of manganese oxides (Ref-Mn) were prepared according to the method developed by (Cole et al., 1947), represented by the reaction (1):



The Mn-B and Mn-NaB were prepared in a weight ratio 1:1 (bentonite: manganese oxides). Ref-Mn was prepared without the addition of bentonites. The process of precipitation included the following steps: Potassium permanganate was dissolved in distilled water in a beaker and kept in a water bath at 90 °C for 15 min. Bentonite was added into the purple solution and this suspension was mixed gently for 10 min. After that 2M HCl was slow added dropwise to the suspension and heated in a water bath at 90°C. After the titration, the mixture was stirred further 30 min. The final product was cooled at the air and washed several times using double distilled water, dried in an oven at 100 °C for 24 hours and stored.

X-Ray diffraction data were obtained by a diffractometer Bruker D8 Advance (40 kV, 40 mA), working with the CuK α radiation. The JCPDS (Joint Committee for Powder Diffraction Data - International Centre for Diffraction Data) database was used to analyze the diffraction peaks.

The infrared spectra were obtained using the KBr disc technique using Nicolet 6700 FTIR spectrometer. For each sample 64 scans were measured in the 4000-400 cm⁻¹ spectral range in the abs mode with a resolution of 4 cm⁻¹.

The overview morphologies and sizes of the particles were obtained by a field emission scanning electron microscope TESCAN MIRA 3 FE SEM with an accelerating voltage of 20 kV. The samples were examined at several magnifications.

Results and discussion

The X – ray diffraction analysis of natural bentonite (B) shows the typical and dominant montmorillonite patterns (Fig. 1a). The natrification of bentonite (NaB) has supported the separation of regular montmorillonite structural layers which leads to the decomposition of its structure and the formation of colloids. Effect of natrification can be observed by the comparison of the montmorillonite basal plane diffractions d_{001} before and after natrification (Fig. 1b). The shift of the d_{001} montmorillonite reflection to the right on the x axis points on the ion exchange in the interlayer space (Na⁺ for Ca²⁺). The shape of the diffraction pattern NaB refers the refinement of structure. Monovalent hydrated cations (Na⁺) are active dispersing the montmorillonite structure (Jelínek et al., 2010). The natrification also facilitates the separation of basic structural layers (Galamboš et al., 2010). All these factors, together with the presence of sodium carbonate and the free surface of the montmorillonite lead to the apparent reduction of the crystallinity after natrification (Figure 1).

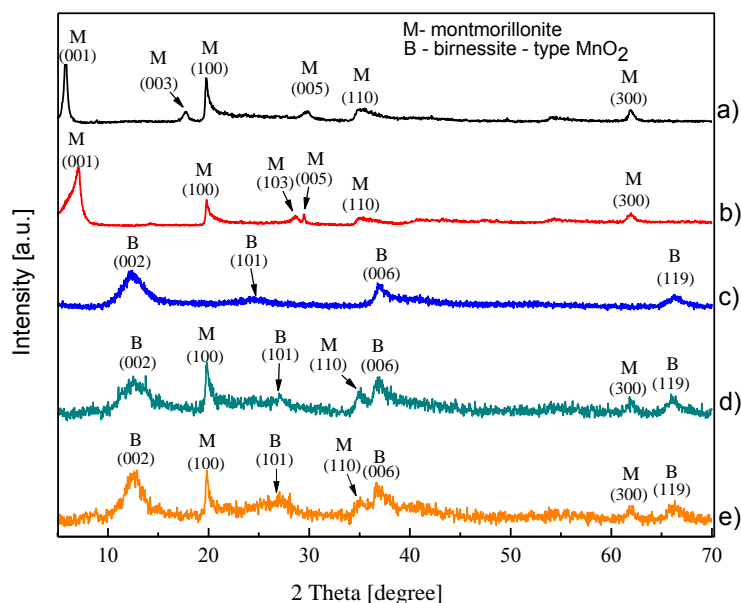


Figure 1. X-ray diffraction patterns of the B (a), NaB (b), Ref-Mn (c), Mn-B (d) and Mn-NaB (e)

The diffraction pattern of a reference sample of manganese oxides (Ref-Mn) is shown in Fig. 1c. Using Database The International Centre for Diffraction Data (ICDD), the diffraction pattern of Ref-Mn most closely approximates to the synthetic birnessite with the characteristic diffraction planes hkl (002), (101), (006) and (119) with empirical a chemical formula MnO_2 (ref. no. 00-018-0802). Identified phase comprises a hexagonal crystal system. Precipitation of manganese oxides on bentonite caused structural changes in both composites Mn-B and Mn-NaB (Fig. 1d,e). The main (001) reflection of montmorillonite was reduced and (005) reflection disappeared. On the diffraction pattern of Mn-B and Mn-NaB can clearly identify the presence of manganese oxide - birnessite type. The positions of diffraction line of manganese oxide - birnessite type in the modified bentonite can be influenced by the presence of various cations (Na^+ , K^+ , Ca^{2+}) and water molecules between the structural layers (Frias et al., 2007).

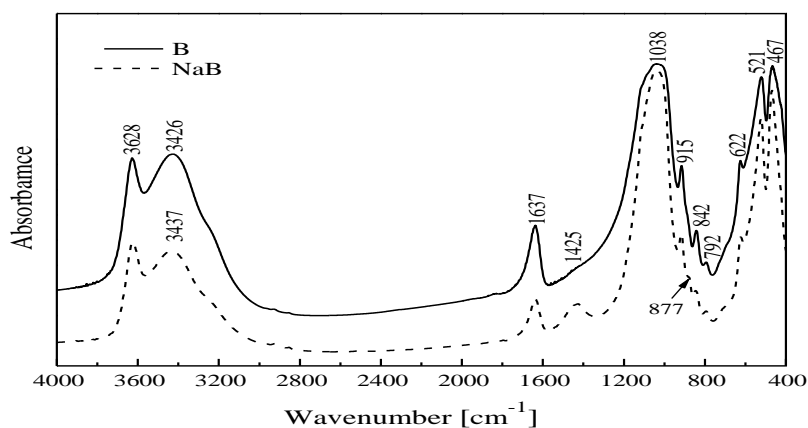



Figure 2. Infrared spectra of B and NaB

In Figure 2 are shown the absorption spectra of B and NaB. The results of the analysis of bentonite (B) were consistent with those of standard samples of bentonite deposits Jelšový potok listed in the database of rocks and minerals Institute of Geonics (Vaculíková, 2008). After natrification of bentonite (NaB) on the IR spectrum discovered traces of carbonates used natrified agent (Fig. 2). In the spectrum (NaB) can be seen to change the position of the vibration surface-bound water; shift of 3426 cm^{-1} to higher wave numbers at 3437 cm^{-1} , this change is probably due to the use natrified agent (Table 1).

Tab. 1 Absorption bands of bentonite infrared spectra

Absorption bands	Bentonite - standard Jelšový potok [114]	B	NaB
OH stretching of structural hydroxyl groups	3625	3628	3627
OH stretching of water	3427	3426	3437
OH deformation of water	1637	1637	1638
traces of carbonates	-	-	1425
Si-O stretching (longitudinal mode)	1114	-	-
Si-O stretching	1037	1038	1040
AlAlOH deformation	914	915	917
traces of carbonates	-	-	877
AlMgOH deformation	842	842	844
SiO stretching of quartz and silica	792	792	791
Si-O	700	-	-
coupled Al-O and Si-O, out-of-plane	623	622	622
Al-O-Si deformation	521	521	523
Si-O-Si deformation	466	467	469

The result of IR analysis of the reference sample of manganese oxides (Ref-Mn) is not exactly to standard MnO₂ published in (Julien and Massot, 2003a; Julien and Massot, 2004b). However, the value of the absorption bands at 520 cm⁻¹ and 468 cm⁻¹ (Fig. 3) generally include bending vibrations O - metal (Mn-O). Moreover, the bands at 3426 cm⁻¹ and 1636 cm⁻¹ belong to the vibration of OH groups of absorbed water molecules. On spectrum of the sample Mn-NaB (Fig. 3) was not observed the traces of carbonates characteristic of the sample NaB (1425 cm⁻¹ and 877 cm⁻¹). The presence of MnO₂ in the pattern of Mn-NaB on the base of vibration bands (520 cm⁻¹ and 468 cm⁻¹) was not possible to confirm. MnO₂ vibrations overlap with the bands of Si-H bonds to the clay mineral (523 cm⁻¹ and 469 cm⁻¹). Interestingly, the intense absorption bands characteristic of the OH vibrations in the structure of montmorillonite at 3621 cm⁻¹ for the sample Mn-NaB proved to be quite "minor arm", suggesting the release of water molecules from the structure of montmorillonite.

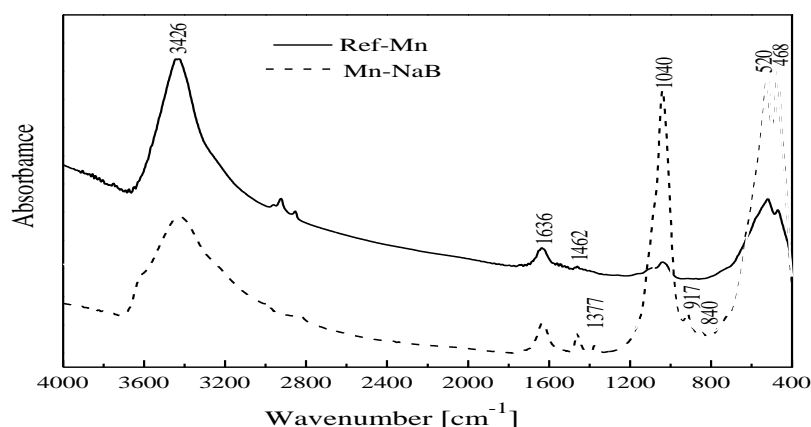**Figure 3.** Infrared spectra of Ref-Mn and Mn-NaB

The natural bentonite (B) was characterized by particle combined in aggregates of a size of several tens μm (Fig 4a). The SEM image of NaB (Fig. 4b) shows that the activation of natural bentonite with sodium resulted in smaller grain sizes caused by the dispersive effect of Na⁺ on the bentonite structure. The SEM analysis of Ref-Mn is shown in Fig. 5. It is characterized the morphology of "sea urchin",

which was formed by a thin nanowall sheets oxide with a thickness of several tens of nanometers (Zhu et al., 2008). These "nanowall sheets" were linked together, arranged randomly, pointing to the center, perpendicular to the sample surface forming a network. Figure 6a and 6b are listed samples of Mn-B and Mn-NaB. The spherical formations of manganese oxides cover the surface of the bentonite particles.

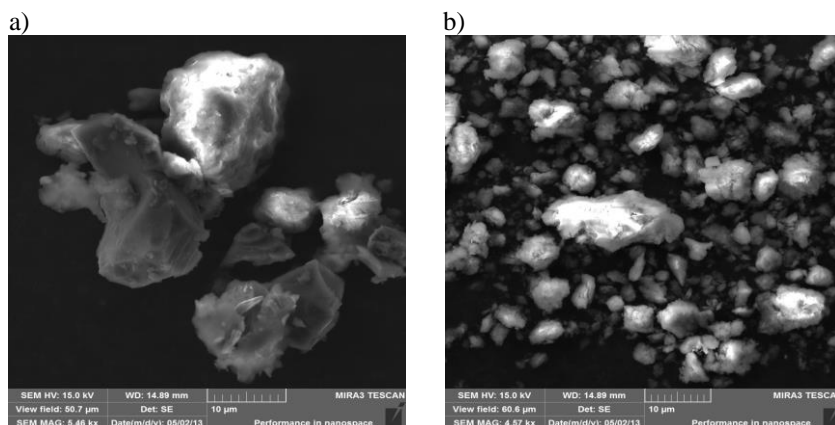


Fig. 4. SEM images of B (a), NaB (b)

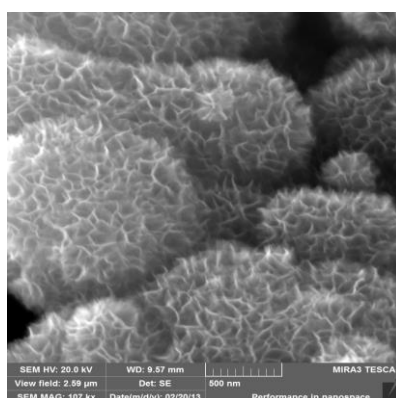


Figure 5. SEM images of Ref-Mn

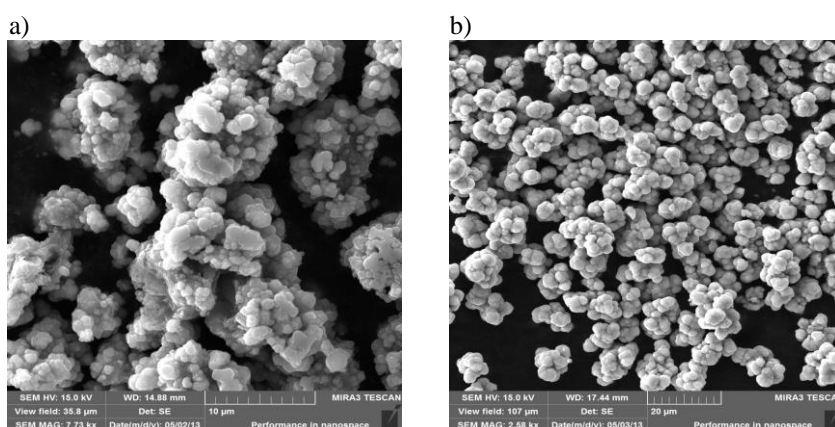


Figure 6. SEM images of Mn-B (a), Mn-NaB (b)

Conclusion

The X-ray diffraction analysis demonstrated the structural changes after natrification of bentonite, related to the exchange of Ca^{2+} cation for Na^+ in the inter-layer space of the montmorillonite structure. The analysis of synthetically prepared reference sample of manganese oxides, showed manganese oxide (MnO_2) with regular birnessite layer structure and hexagonal crystal system. This type of structure MnO_2 was present in all samples modified with manganese. The study of the Mn-B and Mn-NaB morphology showed the manganese oxides covering the small particles of bentonite.

Acknowledgements

This work was supported by the Slovak Grant Agency for Science VEGA grant No. 2/0114/13.

References

- [1] COLE, W. F. et al. 1947. An X-Ray Diffraction Study of Manganese Dioxide. In *Journal of the Electrochemical Society*, 92 (1), 1947, p. 133-158.
- [2] EREN, E. et al. Removal of copper ions by modified Unye clay Turkey. In *Journal of Hazardous Materials*, 159, 2008a, p. 235-244.
- [3] EREN, E. et al. Removal of lead ions by acid activated and manganese oxide-coated bentonite. In *Journal of Hazardous Materials*, 161, 2009b, p. 677-685.
- [4] FAN, H.-J. et al. Copper and cadmium removal by Mn oxide-coated granular activated carbon. In *Separation and Purification Technology*, 45, 2005, p. 61-67.
- [5] FRÍAS, D. et al. Synthesis and characterization of cryptomelane – and birnessite – type oxides: Precursor effect. In *Materials Characterization*, 58 (8-9), 2007, p. 776-781.
- [6] FUSOVÁ, L. et al. The investigation on Pb^{2+} and Cu^{2+} ions on bentonite. In *Inžynieria Mineralna*, 7 (1), 2011a, p. 11-18.
- [7] FUSOVÁ, L., et al. Utilization of Bentonite and Its Modification for Sorption. In *Środkowo-pomorskie towarzystwo naukowe ochrony Środowiska : Rocznik Ochrona Środowiska*, 2011b, p. 163-172.
- [8] GALAMBOŠ, M. et al. Adsorption of cesium and strontium on natrified bentonites. In *Journal of Radioanalytical and Nuclear Chemistry*, 283 (3), 2010, p. 803-813.
- [9] JELÍNEK, P. Iontová výměna u montmorillonitických jíílů a její důsledky. In: *XII. Konferencja Odlewnicza Technical: Zbornik príspevkov*. Nowa Sól: Technical Sp. zo.o. Nowa Sól, 2010. s. 119-126.
- [10] JESENÁK, K. and HLAVATÝ, V. Laboratory device for sedimentation of fine bentonite fractions. In: *Scripta Fac. Sci. Nat. Univ. Masaryk. Brun.*, *Geology*, 28 -29, 2000, p. 33-36.
- [11] JULIEN, C.M. and MASSOT, M. Lattice vibrations of materials for lithium rechargeable batteries I. Lithium manganese oxide spinel. In *Materials Science and Engineering B*, 97 (3), 2003a, p. 217-230.
- [12] JULIEN, C.M. and MASSOT, M. Vibrational spectroscopy of electrode materials for rechargeable lithium batteries III. Oxide Frameworks. In: *International Workshop „Advanced Techniques for Energy Sources Investigation and Testing“: Proceedings*, Bulharsko: Institute of Electrochemistry and Energy Systems, Sofia, 2004b, p. 1-17.
- [13] NOÉMI, M. Nagy et al. Study of the change in the properties of Mn-bentonite by aging. In *Journal of Colloid and Interface Science*, 278, 2004, p. 166-172.
- [14] VACULÍKOVÁ, L. Nové možnosti identifikace jíílových minerálů a slíd v sedimentárních horninách metodou infračervené spektroskopie s Fourierovou transformací: Závěrečná správa k post - doktorskému grantovému projektu GAČR, Ostrava, 105/03/D079, 2008.
- [15] ZHU, H. et al. Birnessite-type MnO_2 Nanowalls and Their Magnetic Properties. In: *Journal of Physical Chemistry C*, roč. 112, č. 44 (2008), 17089-17094.